

Camshafts

Nitriding



Camshafts are exposed to surface wear and fatigue. To meet the demands of the surface, camshafts are generally produced from steel that has been designed for nitriding. The objective is to provide a material that will nitride in a cost effective way and give good surface hardness coupled with a good supporting base material.

The oldest and most well known UK specification is EN40B now called 722M24 and another alternative might be 897M39.

Where 'clean steel' is a pre-requisite then the most commonly used material is S132. Other grades are available where companies have developed specifications to overcome specific problems associated with either mechanical properties or processing. OvaX 200 is our advanced material to meet this need.

OvaX 200

Today at Ovako we have designed a modern alloy steel alternative specifically developed for nitriding. OvaX 200 is a perfect steel for plasma, gas or nitro-carburising.

The material has been designed to give:

- High Cleanliness
- Slow Air Cooling
- Very Low Distortion
- Reduced Grinding and Finishing
- Temper Resistance
- High Operating Temperature

Chemical composition


| Element | C | Si | Mn | P | S | Cr | Ni | Mo | V | O | Ti |
|---------|------|------|------|-------|-------|------|------|------|------|-------|--------|
| Min. | 0.14 | | 1.20 | | | 2.10 | 0.45 | 0.45 | 0.15 | | |
| Max. | 0.17 | 0.15 | 1.40 | 0.020 | 0.003 | 2.30 | 0.55 | 0.55 | 0.25 | 9 ppm | 30 ppm |

Delivery Condition & Machining


We do not normally recommend that the material be delivered with a conventional hardness of between 190-220 HB. While the material will be very suitable for cold or warm forging the structure will be too tough for normal machining since it will have an impact strength of 240 J.

The material is naturally produced with a hardness of approximately 350 HB. The material is in an air quenched & self-tempered condition with a martensitic structure but is capable of being machined directly with standard coated carbide cutting tools.


However, the steel could easily be tempered back to a hardness of between 270-300 HB and can be machined with conventional carbide tooling quite easily at this hardness due to its good structure.

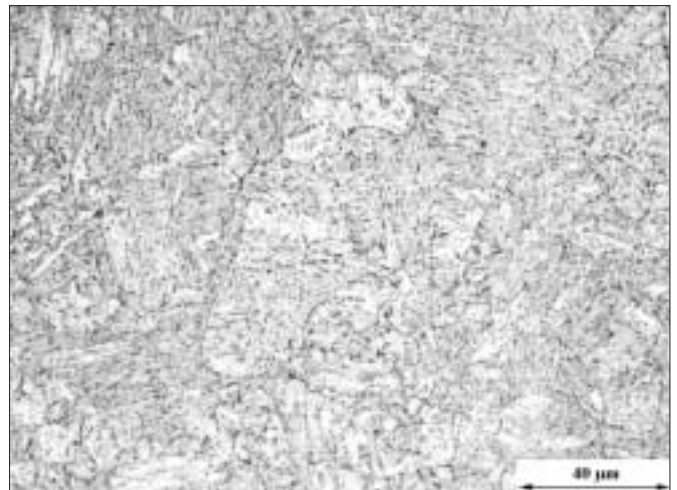

Tough tempered OvaX 200.

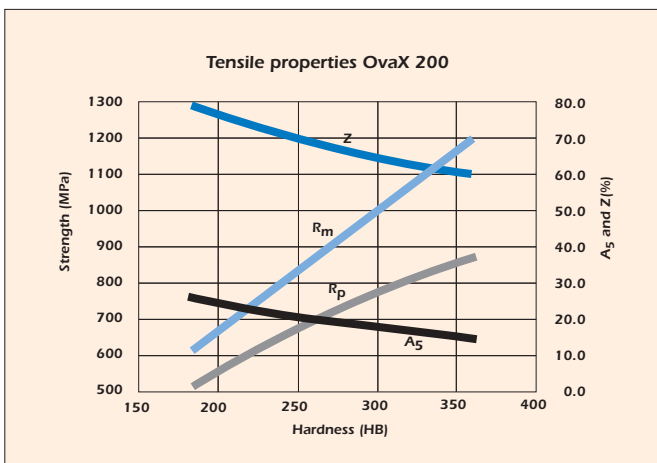

Tensile properties as function of hardness.

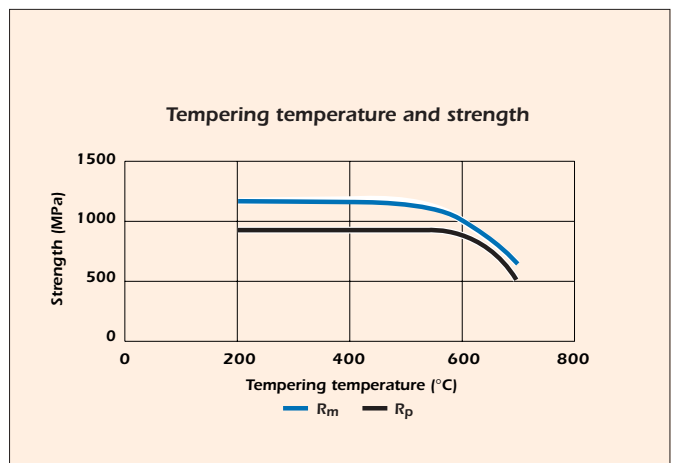

Tensile strength as function of tempering temperatures.

After machining OvaX 200 could be either conventionally hardened and tempered to give a hardness of 380-400 HB or air-hardened and tempered to give a hardness of about 350 HB. The low distortion characteristics of the steel will be lost by con-


ventional hardening since the distortion is primarily a function of quenching speed. Tempering should be made at a suitable temperature dependant on the subsequent nitriding temperature.

Nitriding Processing

The nitriding process is used on OvaX 200 to give a surface hardness of about 850 HV with core hardness levels of between 350-400 HB. The time taken is usually about 20 hours but can be extended if deeper hardness levels are needed.

Nitriding of OvaX 200 can be easily undertaken using either gas or plasma and the process temperatures used are normally at 490° C or 510° C respectively. At this temperature the base material will retain its original properties.

Gas Nitriding

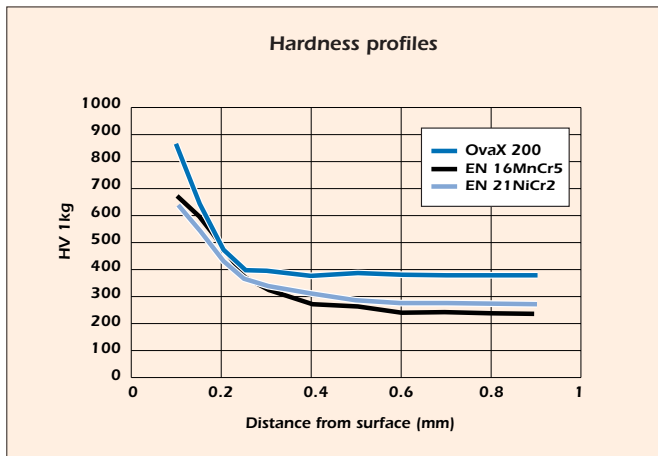


Hardness profiles after gas nitriding of OvaX 200 and two conventional carburising steels.




The microstructure of gas nitrided OvaX 200. The core is tempered martensite and then a diffusion zone and closest to the surface is the compound layer.

Plasma Nitriding

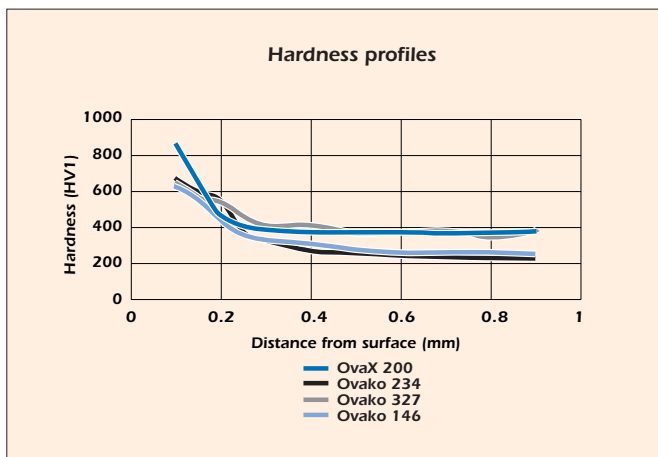

The hardness profiles after plasma nitriding of OvaX 200 and some conventional steels.

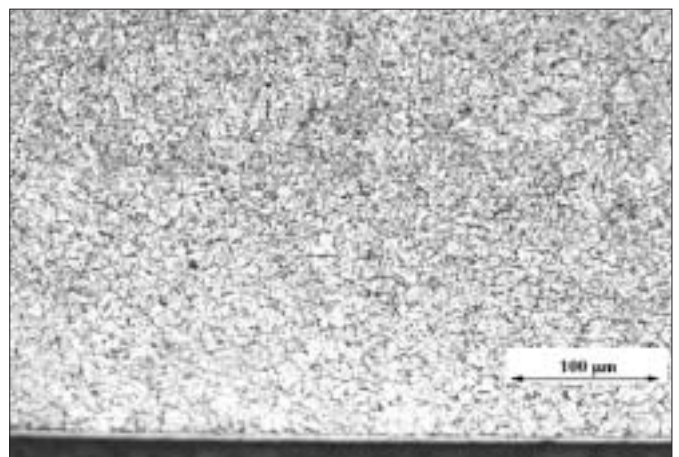


The plasma nitrided microstructure of OvaX 200.

Nitrocarburisation

If nitrocarburising is the favoured route then the higher processing temperature of about 570° C

might have a very slight effect on the overall strength but the structure will be good.

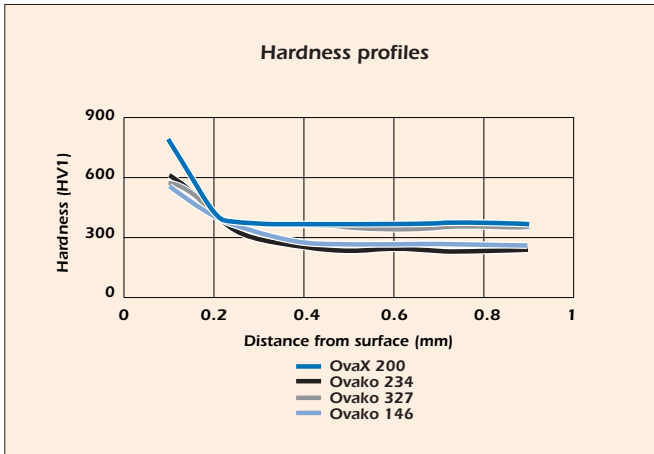

The hardness profiles after nitrocarburising of OvaX 200 and some conventional steels.



The nitrocarburised microstructure of OvaX 200.

OvaX 200 is a superb nitriding steel and offers a very high cleanliness profile enabling it to be used in high performance camshaft applications. In addition the control of distortion offers excellent processing properties and the material gives improved high temperature operation.

Disclaimer

The information contained on this data sheet is provided without any warranty by Ovako of the accuracy of the information or the suitability of any product for any particular use. While Ovako believes that it has taken care to assemble the information, the information is furnished "as is". Ovako warns readers of the data sheet that they should not rely upon the information without separate written confirmation from Ovako, and Ovako therefore excludes any liability, including for negligence and other allegedly tortuous conduct, based upon the information set forth.



Smiths High Performance
Unit O, Stratton Business Park
London Road
Bigglesworth, Beds. SG18 8QB
Tel.: 01767 60 4708
Fax: 01767 31 2885
E-mail: info@smithshp.com
www.smithshp.com



Ovako Ltd.
Unit 2, Britannia Park
Tident Drive, Wednesbury
West Midlands WS10 7XA
Tel.: 0121-502 1010
Fax: 0121-505 0019

www.ovako.com